




Eliminate Gel Coat Porosity  
with SIPERNAT® 22 LS

Every year, imperfections due to gel coat porosity result in substantial losses for composite manufacturers due to unacceptable parts and warranty claims. Porosity is also a problem in unsaturated polyester (UPE) repair pastes and putties where higher labor costs result. There are potentially many causes for porosity in UPE gel coats. High viscosity, gel coat thickness, cure time, air release agent loading, peroxide H<sub>2</sub>O<sub>2</sub> content, spray gun operation/over-pressurization and filler loading are some of the common causes. These causes are easily corrected through proper manufacturing technique by the OEM and/or correct additive formulation by the gel coat supplier. Another major cause for the creation of porosity is the type of thixotrope utilized in the formulation. Products such as organo-clays and fumed silica are known to create porosity in UPE gel coats. The use of SIPERNAT® 22 LS can reduce gel coat porosity in filled UPE products. Due to its unique morphology and surface chemistry, SIPERNAT® 22 LS is able to allow air release while being able to provide rheology comparable to systems that use fumed silica.

Problems caused by gel coat porosity include blistering and accelerated UV degradation. In a marine environment or other liquid contact applications such as storage tanks, high porosity can cause an increase in osmotic blisters due to easier penetration of liquids.

Even resins with high chemical resistance can be undermined by porosity. Because of porosity, blistering can also occur in non-marine applications. Internal porosity can trap gasses that will expand as a result of heating and will eventually create enough pressure to cause the gel coat to blister. This is a particularly big problem in climates with a lot of sunlight and even worse with darker color gel coats. Additionally, porosity can also lead to accelerated UV degradation because of the increased surface area amount. The UV radiation is focused in the external porosity pockets and a faster rate of photo-initiation ensues. Finally, waxes, cleaners, dirt, and other foreign substances can collect in the pits, further accelerating the degradation. Figure 1 displays what typical external porosity looks like in a gel coat.

**Figure 1**  
External Porosity

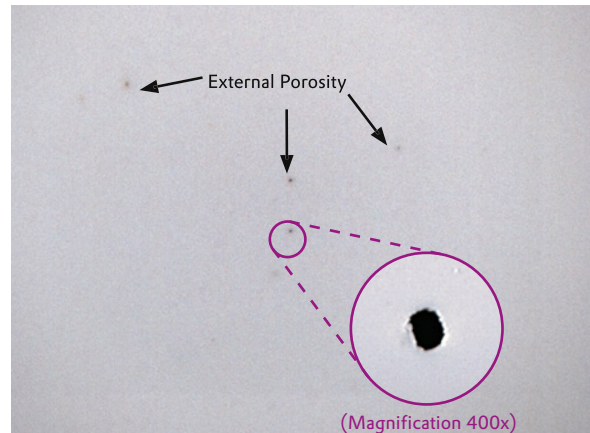

Magnification 40x


Whether reworking a boat or completing body repairs on a car, avoiding pin holes and air bubbles is key to a first class finish. Sanding and buffing a gel coat, or putty, can expose internal porosity as displayed in Figure 2. Examination under microscope of sanded gel coats has become a standard test for sophisticated OEMs such as windmill manufacturers. SIPERNAT® 22 LS can help reduce the internal porosity as well, allowing for the first class, weather resistant finish sought after in industry.

A gel coat with fumed silica, Figure 3, and a gel coat with SIPERNAT® 22 LS, Figure 4, were compared. Both gel coats were prepared the same way. 0.20% BYK A-555 air release agent was dispersed in a low molecular weight UPE resin. The samples were then mixed with either 1.5% fumed silica or 3.0% SIPERNAT® 22 LS, which provides a similar rheology. A small amount of colorant was also added to aid in diagnosing the porosity. Finally, 0.10% Cobalt (12%) promoter was added. Prior to draw down, the samples were initiated with 1.2% methyl-ethyl ketone peroxide.

The figures were obtained using a microscope at 40x magnification. The brown and black dots are air bubbles trapped on the gel coat surface. The pictures illustrate the differences in porosity between Evonik SIPERNAT® 22 LS and fumed silica. The fumed sample in Figure 3 has a much higher degree of porosity than the SIPERNAT® 22 LS sample shown in Figure 4. In a competitive market that is always seeking the best quality product, this improvement can lead to a higher quality gel coat that resists blistering and UV degradation.

Regardless of the application, SIPERNAT® 22 LS can help improve the finish of coatings, and quality of putties, that have imperfections caused by porosity. In order to produce a well rounded optimized gel system, blends of AEROSIL® 200 and SIPERNAT® 22 LS are typically utilized for rheology control. AEROSIL® 200 has been a long time industry standard in unsaturated polyester resin and is essential for creating long term viscosity stability. Looking to improve quality and cost, contact Evonik Industries AG for assistance in improving your UPE formulations.

**Figure 2**  
Internal Porosity

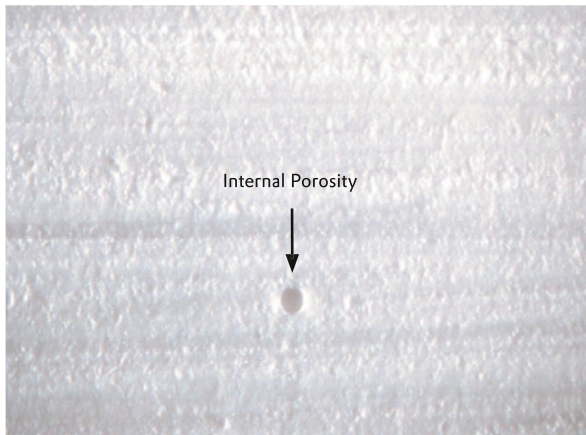

Magnification 400x

**Figure 3**  
Fumed Sample



Magnification 40x

**Figure 4**  
SIPERNAT® 22 LS Sample



Magnification 40x

**Europe, Middle-East, Africa,  
Latin America**

**Evonik Resource Efficiency GmbH**

Business Line Silica  
Rodenbacher Chaussee 4  
63457 Hanau  
Germany

**PHONE** +49 6181 59-12532

**FAX** +49 6181 59-712532

[ask-si@evonik.com](mailto:ask-si@evonik.com)

**North America**

**Evonik Corporation**

Business Line Silica  
299 Jefferson Road  
Parsippany, NJ 07054-0677  
USA

**PHONE** +1 800 233-8052

**FAX** +1 973 929-8502

[ask-si-nafta@evonik.com](mailto:ask-si-nafta@evonik.com)

**Asia (excluding Japan)**

**Evonik (SEA) Pte. Ltd.**

Business Line Silica  
3 International Business Park  
Nordic European Centre, #07-18  
Singapore 609927

**PHONE** +65 6809-6877

**FAX** +65 6809-6677

[ask-si-asia@evonik.com](mailto:ask-si-asia@evonik.com)

**Japan**

**NIPPON AEROSIL CO., LTD**

Marketing & Sales Division  
P.O. Box 7015  
Shinjuku Monolith 13F  
3-1, Nishi-Shinjuku 2-chrome  
Shinjuku-ku, Tokyo  
163-0913 Japan

**PHONE** +81 3 3342-1789

**FAX** +81 3 3342-1761

[infonac@evonik.com](mailto:infonac@evonik.com)

This information and any recommendations, technical or otherwise, are presented in good faith and believed to be correct as of the date prepared. Recipients of this information and recommendations must make their own determination as to its suitability for their purposes. In no event shall Evonik assume liability for damages or losses of any kind or nature that result from the use of or reliance upon this information and recommendations. EVONIK EXPRESSLY DISCLAIMS ANY REPRESENTATIONS AND WARRANTIES OF ANY KIND, WHETHER EXPRESS OR IMPLIED, AS TO THE ACCURACY, COMPLETENESS, NON-INFRINGEMENT, MERCHANTABILITY AND/OR FITNESS FOR A PARTICULAR PURPOSE (EVEN IF EVONIK IS AWARE OF SUCH PURPOSE) WITH RESPECT TO ANY INFORMATION AND RECOMMENDATIONS PROVIDED. Reference to any trade names used by other companies is neither a recommendation nor an endorsement of the corresponding product, and does not imply that similar products could not be used. Evonik reserves the right to make any changes to the information and/or recommendations at any time, without prior or subsequent notice.

SIPERNAT® is a registered trademark of Evonik Industries AG or its subsidiaries.



**EVONIK**  
INDUSTRIES

**Evonik Resource Efficiency GmbH**

Business Line Silica  
Rodenbacher Chaussee 4  
63457 Hanau  
Germany

**PHONE** +49 6181 59-12532

**FAX** +49 6181 59-712532

[ask-si@evonik.com](mailto:ask-si@evonik.com)

[www.evonik.com](http://www.evonik.com)

**Evonik. Power to create.**